

Study of Normal and Superconducting States of MgCNi_3 upon Fe and Co Substitution and External Pressure

T. Geetha Kumary, J. Janaki, Awadhesh Mani, S. Mathi Jaya,

V. S. Sastry, Y. Hariharan, T. S. Radhakrishnan and M. C. Valsakumar*

Materials Science Division, Indira Gandhi centre for Atomic Research, Kalpakkam 603 102, India

(Dated: February 6, 2008)

Results of our study on the superconducting and normal state properties of the recently discovered superconductor MgCNi_3 , the effect of Fe and Co substitution at the Ni site and the effect of pressure are reported. It is shown that a two band model provides a consistent interpretation of the temperature dependence of the normal state resistance and the Hall constant. Whereas band structure calculations suggest an increase in T_c upon partial substitution of Ni with Fe and Co, Co substitution quenches superconductivity and Fe substitution leads to an increase followed by a decrease in T_c . The observed variation of T_c may be explained in terms of a competition between increase in T_c due to increase in density of states and a decrease due to spin fluctuations. Based on these results, it is suggested that the spin fluctuations are weaker in Fe doped samples as compared to the Co doped ones. An initial decrease in T_c (and the normal state resistance) followed by an increase is observed on application of pressure. The decrease in T_c for small applied pressures can be understood in terms of the decrease in the density of states at the Fermi level. The subsequent increase in T_c with pressure is due to a lattice softening or a structural phase transition, consistent with the band structure calculations. It is conjectured that suppression of spin fluctuations by pressure may also be responsible for the observed increase in T_c at higher pressures.

PACS numbers: 74.25.Fy, 74.25.Jb, 74.62.-c, 74.62.Dh, 74.62.Fj

I. INTRODUCTION

The recent discovery¹ of superconductivity in the intermetallic compound MgCNi_3 has initiated a number of studies aimed at elucidating the nature of its normal and superconducting states. Apart from the fact that it is the first known superconducting compound which has a perovskite structure without oxygen, the interest is mainly due to the preference of superconductivity over ferromagnetism which is rather unexpected in a compound whose main ingredient is Ni. By proposing an electronic analogy with the superconducting oxide perovskites, He *et al.*¹ suggested that holes in the Ni d-states might be responsible for electrical conduction in this compound. The signs of the measured Hall constant² and thermoelectric power³ are, however, consistent with normal state transport occurring mainly due to electron-like carriers. Most of the normal state transport properties, like the electrical resistivity $\rho(T)$, Hall coefficient $R_H(T)$ and thermoelectric power $S(T)$, show unusual temperature dependence. They are not amenable to a single unified description encompassing the low and high temperature regimes. For example, the Hall coefficient is almost temperature independent below 140K, but, its magnitude decreases² with increase in temperature above 140K. Even though the conventional Bloch-Gruneisen expression provides a good fit above 70K, a power law seems² to be better for $\rho(T)$ below 70K. An electronic crossover occurring at $T_* \sim 50\text{K}$ was proposed³ to account for these anomalies. The normal state NMR properties of MgCNi_3 are also anomalous⁴ and similar to what is seen in the exotic superconductor Sr_2RuO_4 . Observation⁵ of a zero bias conductance peak in the tunneling spectrum is ar-

gued to be a signature of unconventional pairing (like in the case of Sr_2RuO_4) in this compound. The NMR measurement⁴ below T_c , on the other hand, shows a coherence peak whose magnetic field dependence is consistent with s-wave pairing. The temperature dependence of the electronic specific heat below T_c is consistent⁶ with the conventional electron-phonon mechanism for superconductivity. Analysis¹ of the specific heat data suggests that this compound is a moderately strong-coupled (electron-phonon coupling constant $\lambda \sim 0.77$) superconductor. The observed² temperature dependence of H_{c2} is typical of a conventional superconductor in the dirty limit. Thus a complete understanding of the superconducting and normal states of this compound is yet to emerge.

There have been a number of first principle electronic structure calculations using Tight Binding Linear Muffin Tin Orbital (TB-LMTO)^{7,8,9}, Full Potential Linear Muffin Tin Orbital (FP-LMTO)¹⁰ and Full Potential Linear Augmented Plane Wave (FP-LAPW)^{11,12,13} methods, within the Local Density Approximation (LDA), to understand the electronic and magnetic properties of MgCNi_3 and related compounds. LDA+U calculations¹⁴ on MgCNi_3 with $U = 5\text{ eV}$ yields essentially the same band structure as that of the LDA, indicating that electron-correlation effects of Ni-3d electrons are unimportant in this compound. This is consistent with the fact that the measured value of the Wilson ratio¹⁵ is only 1.15, typical of a system with modest electron-correlation effects. The results of these calculations are quite sensitive to the methods employed and also to the numerical values of the parameters. The general features of the band structure (which, however, are essentially the same

in all these calculations) can be briefly summarised as follows: There is a strong hybridisation between the Ni-3d electrons and the C-2p electrons and thus carbon plays the crucial role of the mediator of electron hopping. Two of the bands cross the Fermi level E_F and hence both of them contribute to conduction. The density of states at the Fermi level ($N(E_F)$) is predominantly due to Ni-3d electrons. One of the distinguishing features of the density of states of this compound is a sharp peak around 50 meV (its location is very sensitive to the method of calculation) below E_F arising from the π anti-bonding states of Ni-3d and C-2p states. The Stoner enhancement¹⁶ is moderately strong to cause ferromagnetic spin fluctuations, but, not strong enough to obtain a ferromagnetic ground state.

It is well known that the perovskite structure is conducive to a variety of interesting physical phenomena like superconductivity, magnetism, colossal magnetoresistance, etc. Soon after the announcement¹ of the discovery of superconductivity in MgCNi_3 , TB-LMTO calculations were performed⁷ to obtain guidelines for synthesis of related compounds with interesting physical properties. The results of the calculations for the pristine MgCNi_3 are consistent with the reports now available in the literature^{8,9,10,11,12,13}. Our calculations showed that MgCMn_3 , MgCFe_3 and MgCCo_3 may form, but they would be magnetic. Replacement of Mg with other alkaline-earth elements Ca, Sr and Ba would be interesting. For example, CaCNi_3 , CaCFe_3 and SrCCo_3 would be magnetic, whereas SrCNi_3 , BaCNi_3 and CaCCo_3 would be nonmagnetic. As mentioned earlier, band structure calculations showed that the Fermi level in MgCNi_3 lies towards the right side of a peak in the Density of States (DOS) $N(E)$. Removal of half an electron per formula unit would shift the Fermi level to the peak in the DOS. Within the rigid band approximation (RBA), this can be achieved by substitution of Ni_3 by $\text{Ni}_{5/2}\text{Co}_{1/2}$ or $\text{Ni}_{11/4}\text{Fe}_{1/4}$. Our spin-polarised supercell calculations for $\text{MgCNi}_{3-x}\text{M}_x$ showed an increase (but much less than the RBA estimate) in $N(E_F)$, and more importantly, *absence* of a magnetic moment, for $x=1/4$ and $1/2$ ($M = \text{Co}$) and $x=1/4$ ($M = \text{Fe}$). Hence an increase in T_c is expected until $x=1/2$ for $M = \text{Co}$ and $x=1/4$ for $M = \text{Fe}$. Furthermore, our calculations suggest a structural instability when the lattice parameter is changed either way. In particular, a lattice instability is conspicuous (in the calculation) at a modest estimated pressure of ~ 2 GPa. Hence effect of application of pressure in this system would also be interesting. In what follows, we present the results of our analysis^{17,18} of the normal state resistance, the variation in superconducting properties upon Fe and Co substitution, and the effect of pressure on the superconducting transition temperature and normal state resistance of MgCNi_3 .

II. SAMPLE PREPARATION AND CHARACTERIZATION

In addition to the pure MgCNi_3 , a series of compounds $\text{MgCNi}_{3-x}\text{M}_x$ ($x = 0.05, 0.15$ and 0.30 for $M = \text{Fe}$; $x=0.05, 0.10, 0.20$ and 0.40 for $M=\text{Co}$) were prepared in order to investigate the effect of hole doping. The samples were prepared by following the solid state reaction route described by He *et. al.*¹. Starting materials used were Mg(99.8%), Ni(99.99%), Fe(99.999%), Co(99.99%) and amorphous carbon(99%), all in the form of powder. 20% excess of Mg is taken in the starting mixture in order to compensate for the loss of Mg due to evaporation. Also an excess of 50% C is taken to obtain the optimum carbon stoichiometry¹ in the compound. The raw materials were mixed thoroughly and were pressed into pellets. The pellets were subjected to the heating schedule described by He *et. al.*¹, in an atmosphere of 92% Ar and 8% H_2 .

The crystal structure of all the samples are characterized by x-ray diffraction. Ac susceptibility and four-probe dc resistance have been measured in the range 4.2K -300K using home-made dip-sticks. The high pressure resistance measurement has been carried out for the pristine MgCNi_3 using a pressure locked opposed Brigman anvils apparatus¹⁹ using the four-probe method. A superconducting Pb manometer is used for pressure calibration. We have also characterized the microstructure of MgCNi_3 with SEM.

III. RESULTS AND DISCUSSION

The x-ray patterns of the undoped and doped samples are consistent with a perovskite structure with the space group $\text{Pm}\bar{3}\text{m}$. Small amounts of unreacted Ni (2-5%) and MgO impurity (<2%) were present in some of the samples. Except for these blemishes, all the samples are of good quality, with sharp x-ray diffraction peaks. The XRD pattern for MgCNi_3 is shown in Fig. 1 as an example. The lattice parameter for the un-substituted MgCNi_3 was found to be $3.810 (\pm 0.0004) \text{ \AA}$ which is in agreement with the values reported in the literature. No significant change in lattice parameter was noticed upon partial substitution of Ni with Fe or Co. This observation is consistent with the very small variation of the lattice parameter, $a(x=0) = 3.806 \text{ \AA}$, $a(x=3) = 3.802 \text{ \AA}$, seen in the study of $\text{MgCNi}_{3-x}\text{Co}_x$ by Ren *et. al.*²⁰.

The variation of resistance R with temperature T of the pristine MgCNi_3 is shown in Fig. 2. It can be seen that the *shape* of the $R(T)$ curve presented here is very similar those reported by He *et. al.*¹ and Li *et. al.*². The residual resistivity ratio of this sample ($R(300\text{K})/R(10\text{K})$) is 2.2 similar to that obtained by He *et. al.*¹. However, the *magnitude* of the resistivity obtained in this study is approximately 30 times more than that of He *et. al.*¹ and 10 times that of Li *et. al.*². This discrepancy can be understood in terms of the possible differences in the

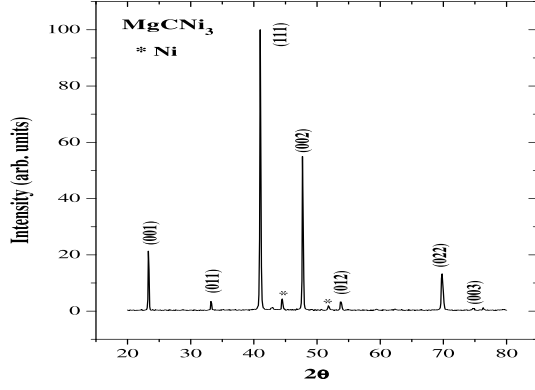


FIG. 1: X-ray diffraction pattern of pristine MgCNi_3 . The lines marked with a * correspond to unreacted Ni.

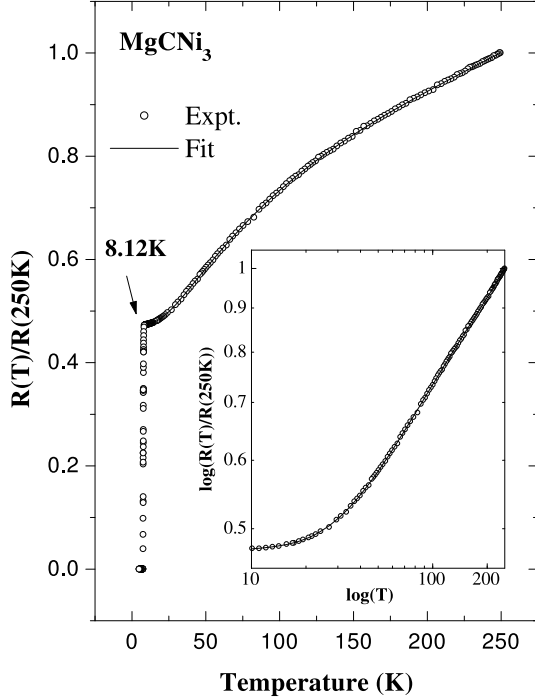


FIG. 2: Resistance as a function of Temperature for pristine MgCNi_3 . The continuous line is a fit to a two band model of conduction. The normal state resistance is plotted as a function of temperature on a log-log scale in the inset to show that the fit is indeed very good in the entire range.

microstructure that can be expected from the fact that unlike in the study of He *et. al.*¹, our samples were not subjected to high pressure sintering. Fig. 3 shows an SEM pattern of one of the MgCNi_3 samples. The fractal character of the sample, which is quite evident from this photograph, entails a much longer and corrugated path (as compared to the bulk) for the electrons. This makes the usual procedure of multiplying the resistance by the (external) Area/Length of the sample to get the resistivity ρ erroneous²¹. Since the actual path length of the electrons in such a poorly connected medium is longer

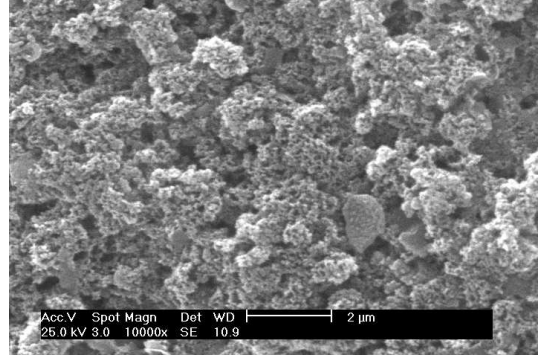


FIG. 3: Microstructure of a MgCNi_3 sample. Fractal like character of the sample can be seen.

than that in the bulk, the apparent resistance will be larger than what is expected from a scaling based merely on the external geometry²¹. Hence there is a need for a geometric renormalisation while converting resistance into resistivity in sintered samples. Our sample is more loosely packed (compared to that of He *et. al.*¹) and hence the larger apparent resistivity of our sample. A superconducting transition with an onset (mid) T_c of 8.13 K (7.69 K) is observed (90-10% of the transition width $\Delta T_c = 0.34\text{K}$). The ac susceptibility measurement (7) shows a lower T_c (onset $T_c = 7.35\text{ K}$) consistent with the values reported in literature¹.

A. Analysis of Normal state Resistance

Assuming compliance with Matheissen's rule, we have tried to fit the normal state resistance of MgCNi_3 with the expression for a conventional metal,

$$R(T) = A + BT^2 + C \left(\frac{T}{\Theta} \right)^5 \int_0^{\left(\frac{\Theta}{T} \right)} dx \frac{x^5}{[(e^x - 1)(1 - e^{-x})]} \quad (1)$$

In Eq. 1, the constant A represents the contribution to resistance from electron-impurity scattering, T^2 term

accounts for the contribution to resistance from electron-electron scattering and also from spin fluctuations, and

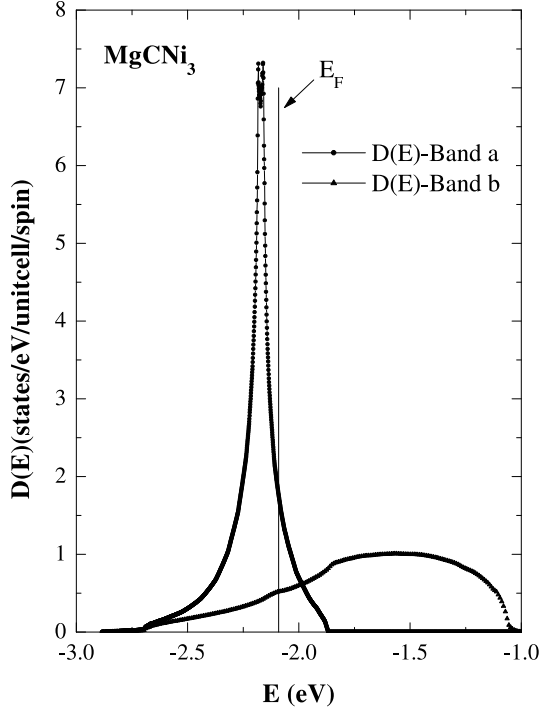


FIG. 4: Density of states corresponding to the two bands that cross the Fermi level. One band is nearly empty and the other is almost full.

last term is the Bloch-Gruneisen integral which represents the electron-phonon scattering. The coefficient B obtained using the fit turns out to be negative and also the fitted value of the Debye temperature ($\Theta \sim 110\text{K}$) is too low. If we substitute this value of Θ and the reported value of the electron phonon coupling constant (λ

$= 0.77$) in the McMillan's formula for T_c given by

$$T_c = \left(\frac{\Theta_D}{1.45} \right) \exp \left(\frac{-1.04(1 + \lambda)}{\lambda - \mu^*(1 + 0.62\lambda)} \right), \quad (2)$$

we get the superconducting transition temperature $T_c \sim 4\text{ K}$, much less than the experimental value (we have taken μ^* to be 0.1).

This and the reported² temperature variation of the Hall constant are consistent with a two band model of conduction involving 'light' electrons coupled to low frequency phonons and 'heavy' holes coupled to high frequency phonons⁷. As mentioned in the Introduction, band structure calculations show that two bands cross the Fermi level (see Fig. 4) one almost full and the other nearly empty. There are equal *number* of electron-like and hole-like charge carriers²² in this compound and the effective mass of the hole-like carrier is almost ten times that of the electron-like carrier. Therefore the normal state electrical conduction will be mainly due to electrons and hence we can expect the Hall constant to be negative. However, both the electrons and holes will be contributing to the conductivity $\sigma(T)$ and hence it will be the sum of the conductivities $\sigma_e(T)$ and $\sigma_h(T)$ due to the electrons and holes, respectively. Therefore the effective resistivity $\rho(T)$ can be written as

$$\rho(T) = A_0 + \frac{\rho_e(T)\rho_h(T)}{\rho_e(T) + \rho_h(T)} \quad (3)$$

where $\rho_e(T) = 1/\sigma_e(T)$ and $\rho_h(T) = 1/\sigma_h(T)$, and A_0 is a constant added to take care of the effect of defects in the sample. In Eq.3 $\rho_e(T)$ and $\rho_h(T)$ have separate temperature dependences,

$$\rho_{e,h} = A_{e,h} + B_{e,h}T^2 + C \left(\frac{T}{\Theta_{e,h}} \right)^5 \int_0^{\left(\frac{\Theta_{e,h}}{T} \right)} dx \frac{x^5}{[(e^x - 1)(1 - e^{-x})]} \quad (4)$$

With B_e and B_h both positive, it is possible to obtain an effective resistivity such that a fit with Eq. 1 would give a negative B .

The continuous line in Fig. 2 is a fit²³ of the normal state resistance, $R(T)$ using the two band model for conduction given by Eq. 3. It can be seen from the figure that the fit is very good (better than 0.15%). Θ_e obtained from the fit is seen to be smaller than Θ_h . That is, the electron-like carriers are coupled to low frequency phonons as compared to hole-like carriers which are coupled to higher frequency phonons. Assuming the value of the hole-phonon coupling constant λ to be the same as that obtained from the specific heat measurement¹, we get a T_c comparable to the experimental value. Thus

we can infer that superconductivity in MgCNi_3 is due to hole-like carriers. Since $\rho_e(T)$ is much less than $\rho_h(T)$, the effective resistivity $\rho(T)$ will be close to $\rho_e(T)$ and hence the value of Θ that one gets with a fit of $\rho(T)$ to Eq. 1 will be close to Θ_e .

The reported variation of the Hall constant $R_H(T)$ can also be qualitatively explained in the two band model. The Hall constant $R_H(T)$ is the weighted sum of the Hall constants R_{He} and R_{Hh} due to the electrons and holes, respectively, and it is given by,

$$R_H = \frac{(R_{He}\sigma_e^2 + R_{Hh}\sigma_h^2)}{(\sigma_e + \sigma_h)^2} = R_{He} \frac{\left[1 - \left(\frac{\rho_e}{\rho_h} \right) \right]}{\left[1 + \left(\frac{\rho_e}{\rho_h} \right) \right]}, \quad (5)$$

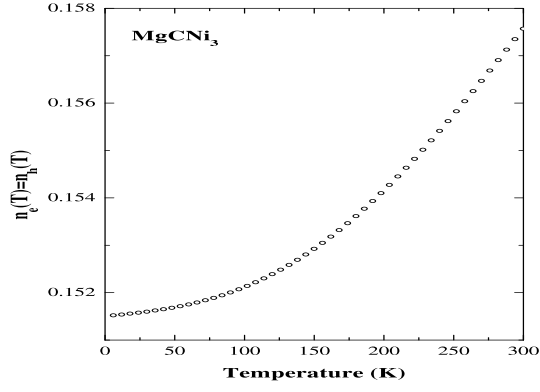


FIG. 5: Temperature dependence of the concentration $n_e(T)$ and $n_h(T)$ of electron-like and hole-like carriers²², respectively. Both of these increase by $\sim 4\%$ when temperature increases from 0 K to 300 K.

Since the number of electrons is equal to the number of holes $R_{Hh} = -R_{He}$ and hence $R_H < 0$. If $\frac{d}{dT} \left(\frac{\rho_e}{\rho_h} \right) > 0$, then the magnitude of R_H also will decrease with temperature thus explaining the reported Hall effect behaviour. We thus see that a consistent interpretation of the temperature dependence of both the normal state resistivity and the Hall constant can be achieved by invoking a two band model of conduction. It remains to be seen whether the same physical picture can provide a satisfactory interpretation of the anomalies seen in the thermopower and NMR relaxation rate.

We have also tried to study the effect of the proximity of the peak in the density of states (van Hove singularity) close to the Fermi level on the resistivity. It is seen⁷ that the chemical potential *increases* with temperature. As a result of this, some of the electrons from the almost filled band go to the almost empty band ($n_b(T)$ increases at the expense of $n_a(T)$ ²²). Thus the numbers of both the electron-like and hole-like carriers increase with temperature. As can be seen from Fig. 5, carrier concentration increases by approximately 4% when the temperature is raised from 0K to 300K. This is one of reasons why the resistivity is not linear in temperature even in the high temperature regime.

B. Effect of Fe and Co substitution

Figs. 6 and 7 represent the superconducting transitions traced by the resistance and susceptibility measurements respectively for the Co substituted compounds. The transition temperature decreases monotonically with increase in Co concentration, similar to the results now available in literature^{20,24}. The variation of the mid point T_c with respect to x , the Co concentration, is shown as an inset of Fig. 6. The decrease in the diamagnetic signal (and hence the superconducting volume fraction) can also be seen in Fig. 7, which again is consistent with the results reported in the literature²⁴. Fe substitution, on

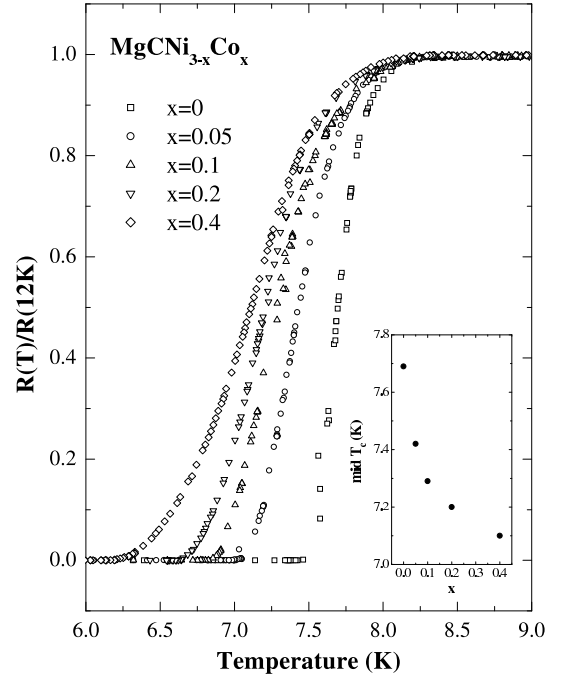


FIG. 6: R vs. T for the Co substituted samples for various concentrations x of Co. T_c decreases and the transition width ΔT_c increases monotonically with x . T_c corresponding to the midpoint of the resistive transition is shown in the inset.

the other hand, leads to an increase T_c followed by a decrease. The superconducting transitions traced for the Fe substituted compounds are shown in Figs. 8 and 9. The maximum T_c is obtained when the Fe concentration is 0.05. The onset of the superconducting transition occurs at 9K for this sample in our resistivity scan. Increasing Fe concentration beyond 0.05 is found to suppress T_c . The inset of Fig. 8 represents the mid point T_c as a function of Fe concentration.

An increase in T_c was expected for Fe substitution till $x=0.25$ and for Co substitution till $x=0.5$, on the basis of a simple minded interpretation of the results of the band structure calculations. However, we observed a monotonic decrease in T_c for Co substitution and an increase followed by a decrease for Fe substitution. These results are clearly at variance with what is expected from the band structure calculations. The observed variation in T_c can be explained in terms of an increase in T_c due to increase in the density of states and a decrease due to spin fluctuations: As mentioned in the Introduction, NMR measurements⁴ have shown existence of ferromagnetic spin fluctuations in MgCNi_3 . Also, magnetic susceptibility measurements have demonstrated that Co doping enhances spin fluctuations in MgCNi_3 ²⁴. If we assume the pairing in MgCNi_3 is of the s-wave type, then it will be suppressed by coupling of electrons (more precisely, the holes) with spin fluctuations. Since we get an increase in T_c for small concentrations of Fe, we believe that the spin fluctuation effect will be relatively less for

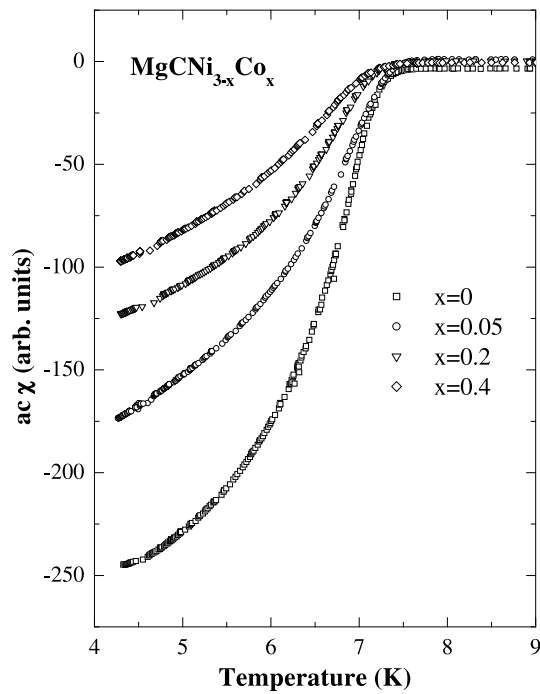


FIG. 7: $ac \chi$ vs. T for the Co substituted samples for various concentrations x of Co. T_c as well as the diamagnetic signal (hence the superconducting volume fraction) decreases with x .

Fe substituted compounds as compared to that of Co substituted ones. This is to be verified experimentally.

C. Effect of Pressure

Figure 10 shows the variation of the total energy as a function of V/V_0 (V_0 is the equilibrium volume) obtained from our band structure calculations⁷. The clear change in slope at $V/V_0 \sim 0.985$ is suggestive of a possible lattice instability. The calculated (using TB-LMTO) bulk moduli of $MgCNi_3$ and fcc Ni are 210 and 250 GPa, respectively. The measured bulk modulus of fcc Ni, on the other hand, is 180 GPa. Thus the LDA calculation overestimates the bulk modulus. We correct for this discrepancy by scaling the calculated bulk modulus by a factor 180/250 (the ratio of the measured and calculated bulk moduli of fcc Ni) and thus estimate the bulk modulus of $MgCNi_3$ to be 151 GPa. With this value of the bulk modulus, we expect the lattice instability to occur at a pressure ~ 2 GPa. It is known that there is no structural or magnetic phase transitions in $MgCNi_3$ as the temperature is varied, at ambient pressure²⁵. But, there is no investigation of the structure of $MgCNi_3$ at high pressure. It would be of interest to do high pressure x-ray diffraction on $MgCNi_3$ to see if the predicted lattice instability indeed occurs or not. Here we report the results of resistivity measurement up to a pressure ~ 7 GPa.

The superconducting transitions and the temperature

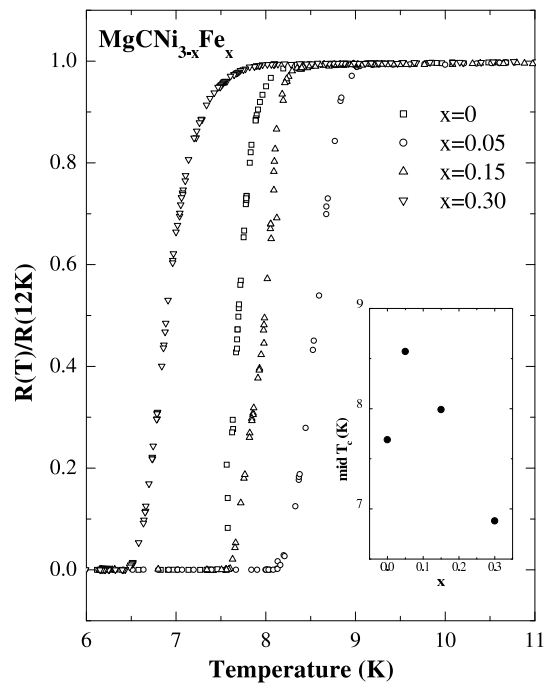


FIG. 8: R vs. T for the Fe substituted samples for various concentrations x of Fe. T_c corresponding to the midpoint of the superconducting transition is shown in the inset. Notice the nonmonotonic behaviour of T_c .

dependence of resistivity of $MgCNi_3$ traced for different external pressures are shown in Fig. 11. T_c is found to decrease with increasing pressure up to ~ 1.7 GPa and it *increases* beyond this pressure. Fig. 12 (a) depicts the variation of the onset T_c with respect to the applied pressure. The normal state resistance also shows a similar trend as can be inferred from Fig. 12 (b) where the variation of the resistance at 10 K is plotted as a function of the applied pressure. Thus the variation of T_c with pressure is consistent with the behaviour expected of a superconductor with the conventional electron(hole)-phonon mechanism- larger the normal state resistivity, higher the T_c . Band structure calculations show a monotonic decrease in $N(E_F)$ with pressure. This would imply a monotonic decrease in the electron-phonon coupling constant λ , if there is no phonon softening. Fit of the resistance to Eq.1 showed an increase in Θ with pressure upto 2 GPa and a decrease there-after. This implies a lattice softening commencing at 2 GPa. If we assume the usual scaling ($\lambda \sim N(E_F)/\Theta^2$) of the electron(hole)-phonon coupling constant with the density of states and the Debye temperature Θ , and calculate T_c using McMillan's formula, we find a variation of T_c with pressure that qualitatively matches with the experimental observation. It is not yet clear whether the decrease in θ with pressure beyond 2 GPa is due to a softening of a particular phonon mode or due to a structural phase transition. Another mechanism that contributes to the increase in T_c would be the suppression of spin fluctuations by pressure,

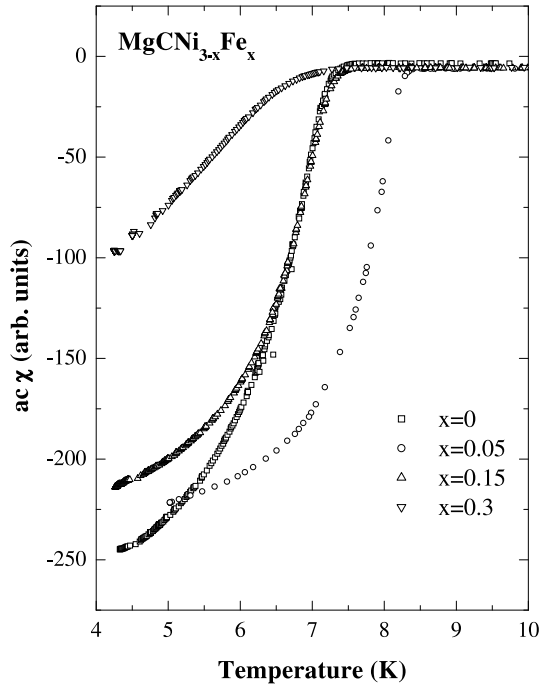


FIG. 9: $ac \chi$ vs. T for the Fe substituted samples

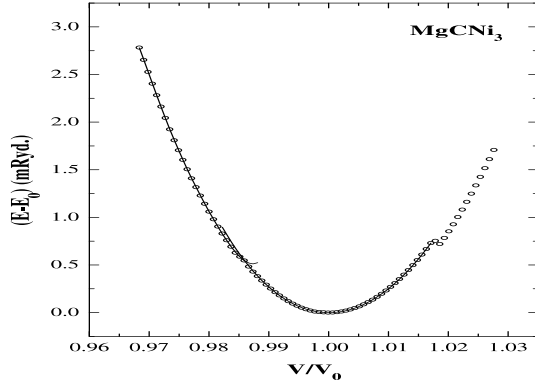


FIG. 10: Total energy of $MgCNi_3$ as a function of V/V_0 , where V_0 is the equilibrium volume, obtained from band structure calculations. Notice the abrupt change of slope near $V/V_0 \sim .985$ as well as the nonmonotonic behaviour near $V/V_0 \sim 1.02$

thereby enhancing pairing.

Before concluding, we would like to touch upon the role of carbon, in relation to superconductivity, in this compound. It is known²⁶ that this compound can form with variable C stoichiometry. However, superconductivity is absent^{1,26} when the C content is less than ~ 0.9 . We have performed band structure calculation (using TB-LMTO) of $MgC_{0.875}Ni_3$ by constructing an appropriate supercell⁷. The density of states at the Fermi level thus calculated is almost the same as that of $MgCNi_3$. Furthermore, $MgC_{0.875}Ni_3$ is non-magnetic as per this spin-polarised calculation. Thus the absence of superconductivity in $MgCNi_3$ below a C concentration ~ 0.9 is also

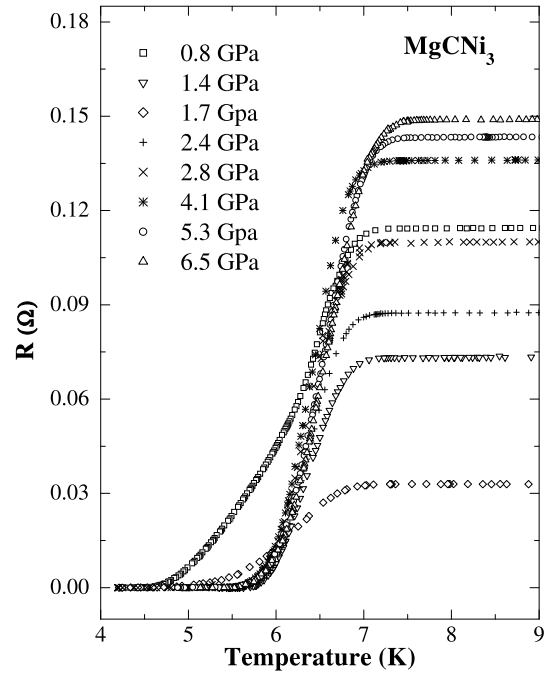


FIG. 11: R vs. T of pure $MgCNi_3$ for various pressures. The normal state resistance decreases until a critical pressure ~ 2 GPa and increases there-after.

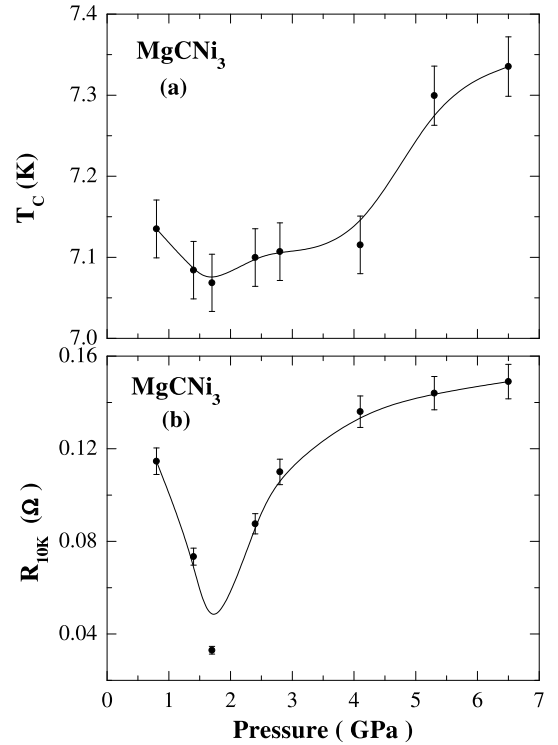


FIG. 12: (a) T_c as a function of pressure; (b) R_{10K} as a function of pressure. Notice the correlation between T_c and R_{10K} .

surprising. We have, however, found a factor of two reduction in the height of the peak in DOS close to the Fermi level. This would support the proposal¹³ of a possible connection between the van Hove singularity and superconductivity in MgCNi₃.

IV. CONCLUSIONS

To conclude, we have synthesised MgCNi₃ and analyzed its superconducting and normal state properties. We have also studied the effect of hole doping at the Ni site and the effect of application of pressure on MgCNi₃. It is found that a two band model for conduction provides a framework for consistently explaining the observed temperature dependence of the normal state resistance and the Hall constant. Co substitution quenches superconductivity, whereas Fe substitution causes an increase in T_c followed by a decrease. This may be understood in terms of a competition between increase in T_c due to increase in the density of states at the Fermi level and a decrease due to spin fluctuations. We specu-

late that spin fluctuations in Fe substituted samples are weaker than in the Co substituted samples. In fact, it is known²⁴ that there is an enhancement of spin fluctuations by Co substitution in MgCNi₃. The observed nonmonotonic variation of T_c with pressure may also be pointing out the importance of spin fluctuations vis-a-vis superconductivity in MgCNi₃. The decrease in T_c for small applied pressures can be understood in terms of the decrease in the density of states at the Fermi level. The subsequent increase in T_c with pressure is suggestive of a lattice softening or a structural phase transition, consistent with the total energy calculations. More experimental and theoretical efforts are needed to understand these issues better.

Acknowledgments

The authors acknowledge Mrs. M. Radhika, Materials Development Division, IGCAR for providing the SEM micrographs of the MgCNi₃ samples.

-
- * email id of the corresponding author: geetha@igcar.ernet.in
- ¹ T. He *et al.*, Nature **411** 54, (2001)
 - ² S. Y. Li *et al.*, Phys. Rev. B **64** 132505, (2001)
 - ³ S. Y. Li *et al.*, cond-mat/0107352 (2001)
 - ⁴ P. M. Singer, T. Imai, T. He, M. A. Hayward and R. J. Cava, Phys. Rev. Lett. **87** 257601, (2001)
 - ⁵ Z. Q. Mao *et al.*, cond-mat/0105280, (2001)
 - ⁶ J. -Y. Lin *et al.*, cond-mat/0202034, (2002)
 - ⁷ M. C. Valsakumar and S. Mathi Jaya, (to be published)
 - ⁸ S. B. Dugdale and T. Jarlborg, Phys. Rev. B **64** 100508(R), (2001)
 - ⁹ J. H. Shim, S. K. Kwon and B. I. Min, Phys. Rev. B **64** 180510(R), (2001)
 - ¹⁰ I. R. Shein, N. I. Medvedeva and A. L. Ivanovskii, cond-mat/0107010, (2001)
 - ¹¹ D. J. Singh and I. I. Mazin, cond-mat/0105577, (2001)
 - ¹² I. G. Kim, J. I. Lee and A. J. Freeman, Phys. Rev. B **65** 064525, (2002)
 - ¹³ H. Rosner, R. Weht, M. D. Johannes, W. E. Pickett and E. Tosatti, Phys. Rev. Lett. **88** 027001, (2002)
 - ¹⁴ Ref. 10 cited in Ref.⁹
 - ¹⁵ Wilson ratio $W = \left(\frac{\chi}{\gamma}\right)_{expt} / \left(\frac{\chi}{\gamma}\right)_{band}$ is defined as the ratio the values of $\left(\frac{\chi}{\gamma}\right)$ obtained from experiment and band theory. χ is the susceptibility and γ is the coefficient of the linear part of the electronic specific heat. $W = 1$ for the uncorrelated case and 2 for the strongly correlated case.
 - ¹⁶ Stoner enhancement $S = 1/(1 - \bar{S})$, with $\bar{S} = I_{ex}N(E_F)$, where I_{ex} is the exchange correlation energy. The system

- will have a ferromagnetic instability whenever $\bar{S} > 1$.
- ¹⁷ T. Geetha Kumary *et al.*, DAE Solid State Physics Symposium, Mumbai, (2001)
- ¹⁸ Awadhesh Mani *et al.*, DAE Solid State Physics Symposium, Mumbai, (2001)
- ¹⁹ Awadhesh Mani *et al.*, in *Proc. Eighteenth International Cryogenic Engineering Conference (ICEC18)* edited by K. G. Narayankhedkar (Narosa Publishing House, New Delhi, 2001) p. 615 (2001)
- ²⁰ Z. A. Ren, G. C. Che, S. L. Jia, H. Chen, Y. M. Ni and Z. X. Zhao, cond-mat/0105366 (2001)
- ²¹ S. B. Arnason, S. P. Herschfield and A. F. Hebard, Phys. Rev. Lett. **81** 3936, (1998)
- ²² Band-a in Fig. 4 is nearly full and band-b is almost empty. Therefore the number of hole-like carriers $n_h(T) = 1 - n_a(T)$ and the number of electron-like carriers $n_e(T) = n_b(T)$, where $n_a(T)$ and $n_b(T)$ are occupancies (per spin) of band-a and band-b, respectively. By virtue of the relation $n_a(T) + n_b(T) = 1$, we find $n_h(T) = n_e(T)$.
- ²³ We have fitted the ratio $R(T)/R(250K)$ so as to eliminate the geometric renormalisation factor that relates the apparent resistivity to the true resistivity
- ²⁴ M. A. Hayward, M. K. Haas, A. P. Ramirez, T. He, K. A. Regan, N. Rogado, K. Inamuru and R. J. Cava, Solid State Commun., **119** 491, (2001)
- ²⁵ Q. Huang *et al.*, cond-mat/0105240, (2001)
- ²⁶ T. G. Amos, Q. Huang, J. W. Lynn, T. He and R. J. Cava, Solid State Commun., **121** 73, (2002)